

Electrical Resistivity and Specific Heat of EuFe_2As_2 Single Crystals: Magnetic homologue of SrFe_2As_2

H. S. Jeevan,^{1,*} Z. Hossain,² Deepa Kasinathan,³ H. Rosner,³ C. Geibel,³ and P. Gegenwart¹

¹*I. Physik. Institut, Georg-August-Universität Göttingen, D-37077 Göttingen, Germany*

²*Department of Physics, Indian Institute of Technology, Kanpur 208016, India*

³*Max-Planck Institute for Chemical Physics of Solids, D-01187 Dresden, Germany*

(Dated: June 24, 2008)

We have grown single crystals of EuFe_2As_2 and investigated its electrical transport and thermodynamic properties. Electrical resistivity and specific heat measurements clearly establish the intrinsic nature of magnetic phase transitions at 20 K and 195 K. While the high temperature phase transition is associated with the itinerant moment of Fe, the low temperature phase transition is due to magnetic order of localized Eu-moments. Band structure calculations point out a very close similarity of the electronic structure with SrFe_2As_2 . Magnetically, the Eu and Fe_2As_2 sublattice are nearly de-coupled.

PACS numbers: 71.20.Eh, 75.20.Hr

I. INTRODUCTION

Investigations of the FeAs based compounds are presently on the rise within the condensed matter community due to relatively high superconducting transition temperatures of electron or hole doped RFeAsO ($\text{R} = \text{La}, \text{Sm}$) and hole doped AFe_2As_2 compounds ($\text{A} = \text{Sr}, \text{Ba}$)^{1,2,3,4,5,6,7}. The FeAs layers common to both series of compounds seem to be responsible for superconductivity. Since superconductivity in this new class of compounds coincides with the disappearance of a spin density wave (SDW) type magnetic transition, spin fluctuations of Fe moments are suggested to play a crucial role in establishing the superconducting ground state in these novel superconductors⁹. The importance of spin fluctuations for unconventional superconductivity has already been realized while discussing the properties of heavy fermion superconductors like CeCu_2Si_2 , CeMn_5 ($\text{M} = \text{Co}, \text{Rh}, \text{Ir}$) as well as high T_c cuprates⁸. Even though we already have numerous superconductors encompassing the whole range of temperature up to 160 K, the discovery of FeAs based superconductors was greeted with great attention primarily due to its apparent non-phononic origin and non-copper based origin. This is the first time that magnetic fluctuations of the "truly magnetic" element iron may produce superconductivity at such a high temperatures.

In RFeAsO compounds, the superconducting transition temperature increases as one substitutes La by smaller rare-earth atoms: T_c rises from 28 K in LaFeAs(O,F) to 52 K in SmFeAs(O,F) ^{1,3}. Very recently, superconductivity has also been reported in RFe_2As_2 compounds for $(\text{K,Ba})\text{Fe}_2\text{As}_2$ and $(\text{K,Sr})\text{Fe}_2\text{As}_2$ with superconducting transition temperatures as high as 38 K. As in the case of RFeAsO , the parent compound RFe_2As_2 also exhibits a spin-density-type phase transition in the temperature range between 160 and 200 K for Ba and Sr compounds which is suppressed by substituting K for the cationic site. The suppression of the SDW transition is

accompanied by the appearance of superconductivity^{4,6}. Just like in BaFe_2As_2 and SrFe_2As_2 the presence of a magnetic transition at 190 K in EuFe_2As_2 [9] was reported more than a decade ago using Mößbauer spectroscopy. From the small value of the hyperfine field the Fe magnetism was suggested to be of itinerant character. Magnetic susceptibility as well as Mößbauer spectroscopy further revealed the magnetic order of localized Eu-moments at 20 K. However, there are no reports of electrical transport or thermodynamic properties on this system yet. Because of the topical interest we have therefore decided to prepare high-quality single crystalline samples and to investigate the phase transitions in this compound using electrical resistivity and specific heat measurements.

II. METHODS

A. Experimental

Single crystals were obtained using a Bridgman method. Starting elements (Eu 99.99%, Fe 99.99 %, As 99.99999%) were taken in an Al_2O_3 crucible which was then sealed in a Ta-crucible under Argon atmosphere. The sample handling was done in a glove box under very pure environment (oxygen < 1 ppm, H_2O < 1 ppm). The sealed crucible was heated under Argon atmosphere at a rate of 30°C/hour to 600°C. The sample was kept at 600°C for 12 hours and then heated to 900°C where again the sample was kept for 1 hour. After this the sample was taken to 1300°C, kept there for 3 hours and then slowly cooled. We obtained several plate-like single crystals using this process. The quality of the single crystals was checked using the Laue method and powder x-ray diffraction as well as scanning electron microscopy equipped with energy dispersive x-ray analysis. Electrical resistivity and specific heat were measured using Physical Properties Measurement System (PPMS, Quantum Design,

USA). Magnetic properties were measured using Superconducting Quantum Interference Device (SQUID) magnetometer procured from Quantum Design, USA.

B. Theoretical

We have performed density functional band structure calculations using two full potential codes: WIEN2K¹¹ and FPLO¹² using the local (spin) density approximation (L(S)DA) including spin-orbit coupling. Additionally, we have included the strong Coulomb repulsion in the Eu $4f$ orbitals on a mean field level using the LSDA+ U approximation applying the atomic-limit double counting scheme. We used the Perdew-Wang¹³ flavor of the exchange correlation potential and the energies were converged on a dense k -mesh with 24^3 points. We used the current experimental lattice parameters. The As position ($z=0.362$) was taken according to Ref. 10. There exists no spectroscopy data for EuFe_2As_2 , therefore we have used a U of 8 eV, standard value for a Eu^{2+} ion. The results were checked for consistency with varying U values.

III. RESULTS AND DISCUSSION

A. Experimental

Powder x-ray diffraction of the crushed single crystals confirms the single-phase nature of the single crystals which form in the ThCr_2Si_2 type tetragonal structure with lattice parameters $a = 3.907(4)\text{\AA}$ and $c = 12.114(3)\text{\AA}$ in good agreement with the values reported in the literature¹⁰. Laue patterns reveal that plate-like single crystals are oriented with their c -axis perpendicular to the plates. The EDAX composition analysis shows that the crystals have uniform compositions with the expected ratio of the elements. There is a tiny percentage of EuAs binary phase in the sample.

Since the magnetic transitions of EuFe_2As_2 have already been reported using magnetic susceptibility and Mößbauer spectroscopy, we focus our investigation on electrical resistivity and specific heat measurements. Fig. 1 shows the specific heat data taken in the temperature range between 2 and 210 K. The low-temperature part of the specific heat shows a lambda-type anomaly with a peak at $T_N = 19\text{ K}$ associated with the magnetic transition of Eu-moments. The magnetic entropy asso-

ciated with this transition is close to $R\ln 8$ as expected for $J = S = 7/2$ Eu^{2+} ions. Even in the presence of a large lattice specific heat background, a clear signature of the high-temperature transition is observed in the form of a very pronounced jump of the specific heat at $T_{SDW} = 195\text{ K}$. This peak reaches a maximum value of more than 50 J/mol K (on top of the phonon contribution) in spite of the small value of the magnetic moment evidenced by the weak hyperfine field¹⁰. The sharp peak would be compatible with a first-order phase transition, similar as found in SrFe_2As_2 ⁵.

Further insight on the phase transitions is obtained from electrical resistivity of the single crystals for the current flowing within the ab -plane (Fig. 2). The electrical resistivity decreases marginally with decreasing temperature down to 200 K. At $\approx 190\text{ K}$, $\rho(T)$ shows a slight upturn leading to a peak before decreasing rapidly with further reduction of temperature. We attribute this increase of the resistivity to the opening of a gap at the Fermi surface due to the formation of the SDW. Similar resistivity signatures have previously been observed at the SDW transitions in e.g. Cr metal¹⁴, URh_2Si_2 ^{15,16} and CeCu_2Si_2 ¹⁷. The fact that the resistivity upturn has not been observed in polycrystalline samples implies an anisotropic temperature dependence of the resistivity at T_{SDW} . Upon lowering the temperature from $\approx 180\text{ K}$ to 20 K the resistivity continues to decrease. At 20 K a further kink is found which results from the

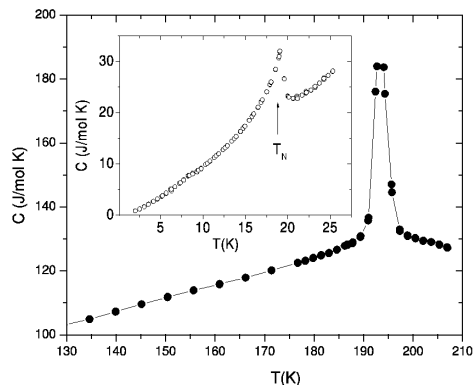


FIG. 1: Temperature dependence of the specific heat of EuFe_2As_2 in the temperature range between 130 and 210 K. The inset shows the low-temperature part from 2 to 25 K. The small bump around 8 K is due to small amounts of EuAs binary phase.

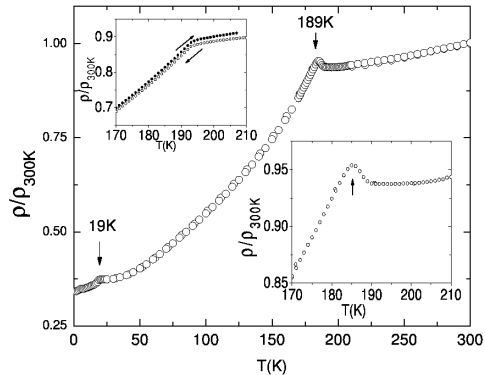


FIG. 2: Temperature dependence of the electrical resistivity of EuFe_2As_2 measured on a plate-like single crystalline sample down to 2 K. The arrow indicate anomalies at 19 and 189 K. The lower inset shows the electrical resistivity data in temperature range between 160 and 210 K. The upper inset shows corresponding data measured on a polycrystalline sample.

ordering of localized Eu-moments. The resistivity ratio $\rho(2\text{K})/\rho(300\text{K}) = 3$ is fairly small but of similar magnitude as found for many 122 compounds crystalizing in the ThCr_2Si_2 type tetragonal structure.

Since EuFe_2As_2 has similar properties compared to BaFe_2As_2 and SrFe_2As_2 , one would like to suppress the Fe magnetism of this compound in order to induce superconductivity. As a first approach we have tried to dope divalent Eu with monovalent K similar to $(\text{K},\text{M})\text{Fe}_2\text{As}_2$ ($\text{M} = \text{Ba}, \text{Sr}$). Our starting composition was $\text{K}_{0.35}\text{Eu}_{0.65}\text{Fe}_2\text{As}_2$. However, our results suggest that a significant part of K evaporated out of the sample due to its high vapor pressure and due to our high-temperature crystal growth method, resulting is a much lower K-content in the sample. We found clear signatures of both magnetic phase transitions in the K-doped sample although the transition temperatures are reduced by a few degrees and the transitions are slightly broadened (not shown) compared to the parent compound. Obviously, we need to improve the doping process in order to suppress the SDW and induce superconductivity.

It is well known that the application of pressure is a suitable tool to change the valence state of Eu from a f^7 configuration to a f^6 state. This transition from Eu^{2+} to Eu^{3+} would provide an additional charge to the FeAs layer as an alternative way to chemical doping. Therefore, a study of the pressure dependence of the Eu valence is very promising.

B. Theoretical

To gain deeper insight into the electronic structure of EuFe_2As_2 and to locate the system within the AFe_2As_2

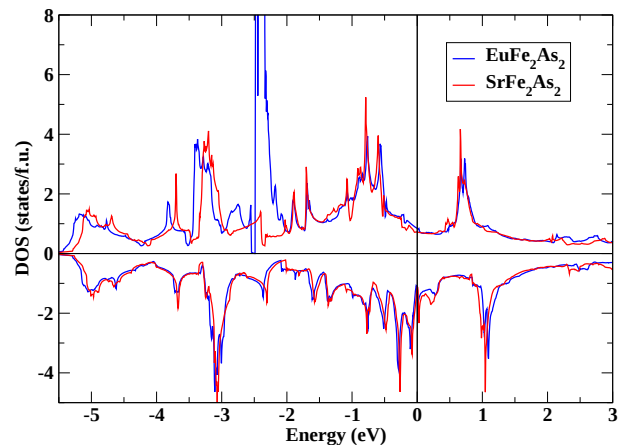


FIG. 3: Comparison of the total DOS for EuFe_2As_2 (LSDA+ U , with ferromagnetic interaction between the Eu and Fe spins) and SrFe_2As_2 (LSDA). The experimental lattice was used for both the compounds. The large peak for the spin-up states at -2.2 eV arises from the fully filled Eu 4 f states. The unfilled Eu 4 f states are at 9.5 eV above the Fermi level.

family we carried out full potential electronic structure calculations within the L(S)DA and LSDA+ U . Usually, for intermetallic Eu compounds, LSDA calculations result in a Eu^{3+} state with the Eu 4 f electrons at the Fermi level ε_F . This well known flaw is in contrast to experimental observations, caused by the underestimation of the strong Coulomb repulsion U for the localized Eu 4 f electrons within the L(S)DA. Adding the Coulomb correlation U on a mean field level using LSDA+ U , the 4 f states split by about U into an occupied an an unoccupied complex. Surprisingly, already the LSDA for EuFe_2As_2 yields a Eu^{2+} state with the occupied Eu 4 f complex at about -0.5 eV and the unoccupied about 4 eV above ε_F . This result suggests a rather stable divalent Eu state and is confirmed by our LSDA+ U where the seven occupied Eu 4 f bands are shifted further down in energy (see Fig. 3).

Apart from the localized Eu 4 f , the resulting electronic density of states (DOS) is almost identical with the DOS of the isovalent SrFe_2As_2 (see Fig. 3), especially for the Fe 3 d states close to ε_F . Within the physically realistic range, this result is independent of the choice of U . The strong similarity between both systems holds even for details of the band structure and the related Fermi surfaces (not shown). To study whether the small differences in the electronic structure arise from the change of structural parameters or from the change of the cation, we calculated the DOS for the crystallographic data of the Eu compound where Eu was replaced by Sr. Comparing the resulting DOS with that of SrFe_2As_2 , we can assign these differences almost exclusively to the change in crystal geometry rather than to the substitution of the magnetic Eu^{2+} ion by Sr.

In SrFe_2As_2 , only the Fe atoms are magnetic, while in

EuFe_2As_2 there are 2 magnetic sub-lattices. This raises the question whether the ordering of the Eu moments around 20 K in EuFe_2As_2 is aided by the interaction with the Fe spins or just due to Eu-Eu interaction. In order to estimate the strength of the Eu and Fe sub-lattice interaction we performed fixed spin moment calculations within the LSDA+ U formalism, for ferromagnetic Eu and Fe sublattices. It is energetically favorable by 2.5 meV/f.u. to have the Eu and Fe moments parallel to each other rather than antiparallel. Since the Eu 4*f* states are quite localized, we can map the energy difference from our fixed spin moment calculations onto a simple Heisenberg model to get an estimate for an effective nearest neighbor exchange (J_{eff}) between the Eu and Fe sub-lattice. We obtain a value of about 1 K for J_{eff} which is rather small compared to the experimental ordering temperature for the Eu moments (≈ 20 K). This implies that the Eu and Fe sub-lattices are quite decoupled in this system.

Furthermore, the inclusion of spin-orbit coupling allows an estimate of the spin anisotropy for the compound. Comparing the total energies for Fe 3*d* spins laying the basal plane (along 100) and Fe spins pointing along the *c* axis (along 001) we find an easy plane anisotropy of about 0.15 meV per Fe site. Our result is consistent with the magnetic structure proposed by recent neutron scattering measurements on the magnetic homologue BaFe_2As_2 ¹⁸. For the $S=7/2$ Eu^{2+} ion, we obtain a negligible (easy axis) anisotropy at the border of numerical accuracy in agreement with the expectations for a spherical half filled 4*f* shell.

To investigate the possibility of a pressure induced va-

lency change of the Eu from 2+ to 3+, we performed a series of calculations for reduced unit cell volumes of EuFe_2As_2 . We maintained a constant *c/a* ratio and a constant As *z* parameter. For up to a 35% reduction of the experimental volume, we did not observe evidence for a change in the valency of the Eu ion. This result suggests that, only for very high pressures of the order of 50 GPa or above a valence change of Eu might be expected.

IV. CONCLUSION

We have grown single crystals of EuFe_2As_2 using a Bridgman technique in a closed Ta crucible. Measurements of the electrical resistivity and the specific heat clearly establish the magnetic ordering of localised Eu moments at $T_N = 20$ K and itinerant Fe moments at $T_{SDW} = 190$ K. Band structure calculations reveal a close similarity of the electronic structure of EuFe_2As_2 and SrFe_2As_2 . The Eu and Fe_2As_2 sub-lattice are nearly de-coupled with Fe spins preferably oriented within the *a* – *b* plane. Our preliminary attempt to dope K in place of Eu did not produce a superconducting ground state. Further doping experiments are highly desirable to study possible superconductivity in this compound and its interplay with the Eu magnetic moments.

The authors would like to thank A. Leithe-Jasper for supplying the KAs compound and U. Burkhardt and P. Scheppen for chemical analysis of the samples. We acknowledge financial support by the DFG Research Unit 960 and BRNS (grant no. 2007/37/28).

-
- * Electronic address: jeevan@cpfs.mpg.de
- ¹ Y. Kamihara, T. Watanabe, M. Hirano, and H. Hosono, J. Am. Chem. Soc. **130**, 3296 (2008).
 - ² H. Takahashi, K. Igawa, K. Arii, Y. Kamihara, M. Hirano, and H. Hosono, Nature **453**, 376 (2008).
 - ³ X.H. Chen, T. Wu, G. Wu, R. H. Liu, H. Chen and D.F. Fang, Nature **453**, 761 (2008).
 - ⁴ G.F. Chen, Z. Li, G. Li, W.Z. Hu, J. Dong, X.D. Zhang, P. Zheng, N.L. Wang and J.L. Luo, *arXiv:0806.1209v1* (2008).
 - ⁵ C. Krellner, N. Caroca-Canales, A. Jesche, H. Rosner, A. Ormeci, and C. Geibel, *arXiv:0806.1043v1* (2008).
 - ⁶ M. Rotter, M. Tegel and D. Johrendt, *arXiv:0805.4630v1* (2008).
 - ⁷ M. Rotter, M. Tegel, I. Schellenberg, W. Hermes, R. Pottgen, and D. Johrendt, Phys. Rev. B **2008**, in press.
 - ⁸ F. Steglich, C. Geibel, F.M. Grosche, M. Loewnhaupt, O. Stockert, S. Wirth, H.Q. Yuan, Physica B **403**, 968 (2008).
 - ⁹ K. Haule, J.H. Shim and G. Kotliar, Phys. Rev. Lett. **100**, 226402 (2008).
 - ¹⁰ H. Raffius, E. Moersen, B.D. Mosel, W. Mueller-Warmuth, W. Jeitschko, L. Terbüchte and T. Vomhof, J. Phys. Chem. Solids **54**, 135 (1993).
 - ¹¹ P. Blaha, K. Schwarz, G.K.H. Madsen, D. Kvasnicka, and J. Luitz, WIEN2K, An augmented planewave+local orbitals program for calculating crystal properties (Technische Universität Wien, 2002, Austria); <http://www.wien2k.at>
 - ¹² K. Koepernik, and H. Eschrig, Phys. Rev. B **59**, 1743 (1999); I. Ophale, K. Koepernik, and H. Eschrig, Phys. Rev. B **60**, 14035 (1999); <http://www.fpld.de>
 - ¹³ J. P. Perdew, and Y. Wang, Phys. Rev. B **45**, 13244 (1992).
 - ¹⁴ O. Rapp, G. Benediktsson, H.U. Astrom, S. Aarjäs and K.V. Rao, Phys. Rev. B **18**, 3665(1978).
 - ¹⁵ T. Ueda, D. Honda, K. Sugiyama, T. Matsuda, N. Metoki, F. Honda, K. Kaneko, Y. Haga, T. Takeuchi, K. Kindo, R. Settai and Y. Ōnuki, Physica B **359-361**, 133(2008).
 - ¹⁶ T.M. Palstra, A.A. Menovsky and J.A. Mydosh, Phys. Rev. B **33**, 6527 (1986).
 - ¹⁷ P. Gegenwart, C. Langhammer, C. Geibel, R. Helfrich, M. Lang, G. Sparn, F. Steglich, R. Horn, L. Donnevert, A. Link and W. Assmus, Phys. Rev. Lett. **81**, 1501 (1998).
 - ¹⁸ Q. Huang, Y. Qiu, Wei Bao, J.W. Lynn, M.A. Green, Y.C. Gasparovic, T. Wu, G. Wu, and X.H. Chen, *arXiv:0806.2776v1* (2008).